



Bio-synthesis of zinc oxide nanoparticles from bitter leaf (*vernonia amygdalina*) extract for dye-sensitized solar cell fabrication

A. N. Ossai¹, S. C. Ezike^{2*}, A. B. Dikko²

¹Department of Physics and Materials Science, Kwara State University, Malete, Kwara State, Nigeria

²Department of Physics, Modibbo Adama University of Technology, Yola, Adamawa State, Nigeria

Received 01 Dec 2019,
Revised 01 Feb 2020,
Accepted 02 Feb 2020

Keywords

- ✓ Bio-synthesis,
- ✓ Zinc oxide,
- ✓ Nanoparticles,
- ✓ Dye-sensitized Solar cell,
- ✓ *Vernonia Amygdalina*.

sabastine.ezike@mautech.edu.ng
Phone: +2348037834194

Abstract

In this paper, we report biosynthesis of Zinc oxide nanoparticles (ZnONPs) from *Vernonia Amygdalina* (bitter leaf) extract. ZnONPs film was deposited on fluorine doped tin oxide (FTO) and characterized using UV visible spectroscopy, Fourier transform infra-red (FTIR) spectroscopy, scanning electron microscopy (SEM) and x-ray diffraction (XRD). Biosynthesized ZnONPs has ~75% absorption at ultraviolet (UV) region. The FTIR spectroscopy shows that ZnONPs was synthesized as peaks at 1650 cm^{-1} and 725 cm^{-1} correspond to Zn-O stretching and deformation vibration, respectively which agreed with previous reports. The photovoltaic (PV) performance of the *Vernonia Amygdalina*-synthesized ZnONPs based Dye-sensitized solar cell (DSSC) was determined and compared with synthetic ZnONPs based DSSC. The synthesized ZnONPs based solar cell demonstrated enhanced power conversion efficiency of 0.63%. This shows that synthesized ZnONPs-based solar cell is found suitable for cost-effective and environmentally friendly energy conversion device.

1. Introduction

The world awareness in green and clean energy is in increase, and solar cells fabricated is expected to be free from environmental pollution [1-4]. The applications of zinc oxide nanoparticles (ZnONPs) in thin-films transistors [5], light emitting devices [6], solar cells [7-9], gas sensors [10,11], biomedical applications [12] and piezoelectric devices [13] are due to its excellent optical and electrical properties [5]. In the family of semiconducting materials, ZnO is known as direct wide band gap at range of 3.2 eV to 3.37 eV and has good transparency [14,15] at room temperature. ZnO could be alternative material for titanium dioxide (TiO₂) due to its non-degrading nature, environmentally friendly and easiness to be synthesized into various shapes and sizes [16]. RF magnetron sputtering [17], chemical vapour deposition [18], pulsed laser deposition [19] thermal chemical vapor deposition [20], sol-gel spincoating [21,22], spray pyrolysis [23] chemical bath deposition [24] etc are used to prepare ZnO thin films.

The need to use non-toxic and environmentally friendly materials in synthesis of ZnO is highly needed as it will reduce environmental hazard. Different physical, chemical and biological methods have been deployed in synthesis of nanoparticles [25-27].

Using various parts of plants in nanoparticle synthesis is novelty as it involves green chemistry which does not need high pressure, temperature, energy and toxic materials [28]. Recently, use of fruit (tomatoes) [5] bacteria, fungus [29] and leaf extract [30] have been reported for ZnO nanoparticles synthesis. The adoption of the eco-friendly benign materials in ZnO synthesis offers many advantages in the environment, pharmaceutical and biomedical applications.

In this work, we synthesized ZnONPs biologically using bitter leaf extract and some characterizations were carried out. Then, the thin film of biosynthesized ZnONPs was deployed as window layer in fabricated dye-sensitized solar cells using black cherry as active layer.

2. Material and Methods

2.1. Preparation of leaf extract of *Vernonia Amygdalina*

Vernonia amygdalina leaves were air-dried for one week. The leaves were crushed with ceramic mortar and pestle into fines powder. 100 ml of ethanol added in 5g of the leaf powder in a beaker and heat the mixture using magnetic stirrer at temperature of 60 °C and 700 rpm for 30 minutes. The solution is filtered using Whatman filter paper and the filtrate is collected for further use.

2.2. Synthesis of ZnONPs.

5g of Zinc Sulphate heptahydrate (Merck) was added to the 15 ml of the leaf extract kept on a magnetic stirrer set at 60°C and 750 rpm and white cloudy appeared. The solution is left for two hours in same condition and overnight incubation at room temperature. Centrifugation at 5000 rpm and 20 minutes, the white pellet is collected and dried in an oven at 150°C. The white dried powder obtained was collected for further use.

2.3. Substrate cleaning

Fluorine doped tin oxide (FTO) glasses were used as transparent substrate. Before usage, they were immersed in distilled water with detergent in an ultrasonic bath for 15minutes at 30 °C with the help of a VWR ultrasonic cleaner (model 07043-986 Symphony). They were then rinsed with distilled water in ultrasonic cleaner at the same condition, later with ethanol at the same condition and lastly, with Isopropyl alcohol at the same condition and dried.

2.4. Preparation of the zinc oxide (ZnO) electrodes.

2.5 g of biosynthesized ZnO was hydrolyzed at 90 °C in 10ml of Isopropyl alcohol and distilled water of same ratio for 40 minutes, respectively. The mixture was mixed using an ultrasonic heat-stir (Stuart heat-stir UC152). Smooth and milky solutions were obtained. The result paste were deposited on fluorine doped tin oxide (FTO) coated glass using a spin-coating machine (WS-650MZ-23NPP Laurell). The deposited ZnONPs thin film was dried on a hot plate at 100 °C for 10 minutes. Later, the film was annealed at 500 °C for 30 minutes in a furnace to increase the adherence between particles and with the FTO layer. Thereafter it was left in the furnace to cool till the next day to avoid cracking of the film.

2.5. Solar cells fabrication

Black cherry fruit (Figure 1) was used as source of natural dye. The cooked black cherry fruits were crushed using mortar and pestle. The dye was filtered out using Whatman filter paper. The absorbance of dyes solutions was characterized using UV-Vis spectrophotometer (JENWAY 6705).



Figure 1: Images of black cherry fruits

Then, the ZnO electrodes were immersed into the dye solutions for 18 hours. The dye solution immersed ZnO electrode was kept in dark room. After, 18 hours, the ZnO substrates adsorbed dye were rinsed in ethanol so as to remove excess dye.

Counter electrode was prepared by scratching 2B pencil (graphite) on the cleaned FTO glass substrate. The electrolyte solution (Iodide/triiodide) was placed at the edges of the plates. The liquid electrolyte was drawn into the space between the electrodes by capillary action. Binder clips were used to hold the electrodes together. I-V measurement was carried using I-V source meter (Keithley 2400).

3. Results and discussion

3.1. Optical properties of ZnONPs Film

Absorption spectrum (Figure 2) shows film characterized at ultraviolet (UV) to visible regions (200 – 800 nm). In the figure, there are strong absorption ($\lambda < 347$ nm) and strong transmittance ($\lambda > 347$ nm) regions which corresponds to the reported by Khan et al. (2017) [22]. The 347 nm marks the transition wavelength from high absorption to low absorption. The average absorption at 200 to 320 nm is ~ 75 %. It is expected that at low absorption, high transmission value of visible light results. At visible range, it was observed that ZnONPs has very low absorption at visible range. The activity of the film shows that it can be used to protect UV radiation in optoelectronic devices since its absorption at the UV region is high [31, 32].

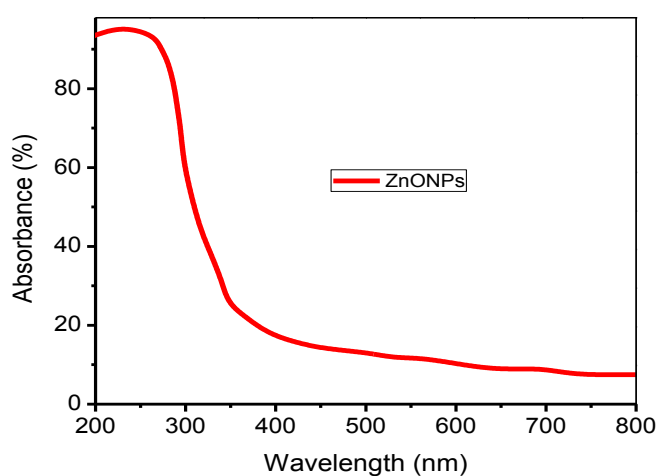


Figure 2: Absorption spectrum of biosynthesized ZnONPs

3.2. Surface morphology characterization

The morphology of the ZnONPs thin film (Figure 3) deposited by solution method was carried out using scanning electron microscope (SEM). It shows that the glass substrate is entirely covered with spherically nanograined ZnO film.

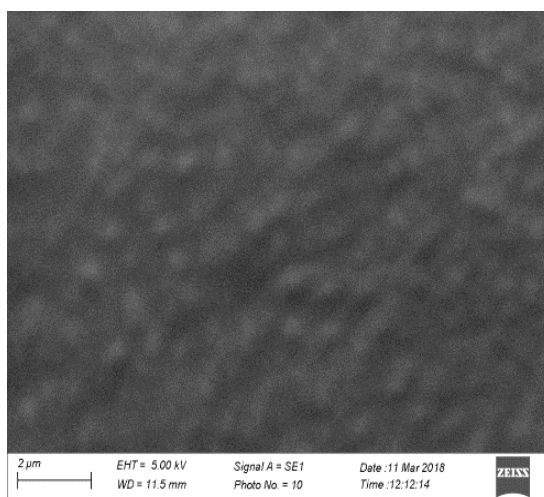


Figure 3: SEM image of ZnONPs thin film.

The SEM micrograph contains uniform size of particles which could be due to low viscosity of the solution [33]. In the film, ZnONPs were dispersed into the ZnONPs thin film. The SEM reveals that the particles are spherical and have granular nature. The morphology of the film shows that the film are uniformly distributed on substrate. The uniform distributed films in the sample could reduce short circuiting in solar cells.

3.3 X-ray diffractometry (XRD) analysis

The XRD of ZnONPs synthesized with bitter leaf is as shown in Figure 4. According to the spectrogram of the crystal structure, the well defined peaks typical of ZnONPs in the crystal structure are clearly noticed. The peaks are in well defined shape and form. This indicates the crystallinity of the biosynthesized ZnONPs. The peaks are indexed as $31.67^\circ(100)$, $34.28^\circ(002)$, $36.43^\circ(101)$, $47.48^\circ(102)$ and $56.46^\circ(211)$, respectively[34, 35]. All diffraction peaks of the sample correspond to the characteristic hexagonal wurtzite structure of ZnONPs ($a = 0.315 \text{ nm}$ and $c = 0.529 \text{ nm}$) [36]. Average particle size of ZnONPs is found to be 9.5 nm according to Scherrer equation [37].

$$D = \frac{0.9 \lambda}{\beta \cos \theta} \quad (1)$$

where λ is the X-ray wavelength, equals to 0.154 nm , θ is the Bragg diffraction angle, and β is the full width half maximum (FWHM) of the XRD peak appearing at the diffraction angle θ . Also, the analysis of ZnO nanoparticle showed that weight percent of 80.34 and 19.66 correspond to zinc and oxygen, respectively. This corresponds to the result gotten from EDX and confirms that ZnONPs was synthesized.

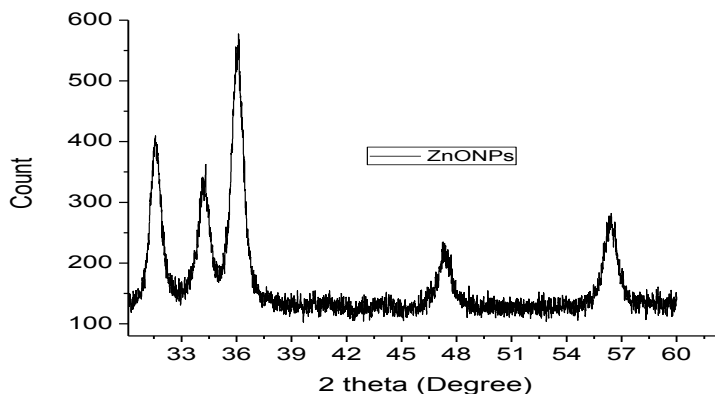


Figure 4: XRD pattern of synthesized ZnONPs

3.4 Energy dispersive x-ray (EDX)

The analysis of the elemental composition of biosynthesized ZONPs (Figure 5) (CBd) using Energy-Dispersive X-ray (EDX). The EDX analysis shows that the compound composed of zinc and oxygen. Zinc has 82.32 weight %, 53.27 atomic % and oxygen has 17.68 weight %, 46.74 atomic %. The revelation of elemental composition of the sample shows that zinc and oxygen are present which confirm that ZnO was actually deposited.

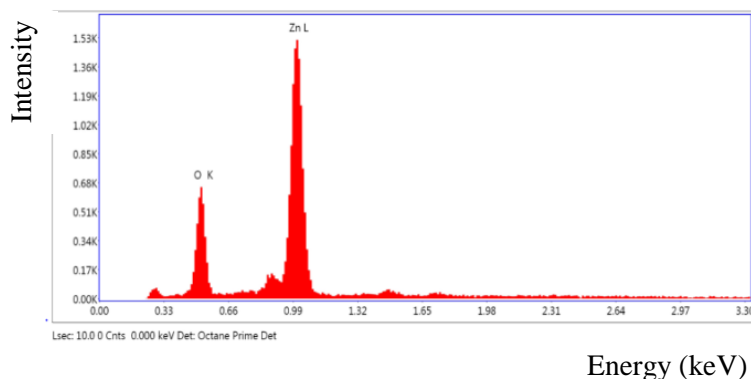


Figure 5: Elemental composition of biosynthesized ZONPs

3.5 Fourier transform infrared spectroscopy (FTIR)

The FTIR spectrogram of biologically synthesized ZNONPs with bitter leaf is shown in Figure 6. The FTIR spectrum was carried out using a spectrometer using KBr pellet technique in the range of 400 – 4000 cm^{-1} to determine the level of purity and ascertain the metal nanoparticle synthesized.

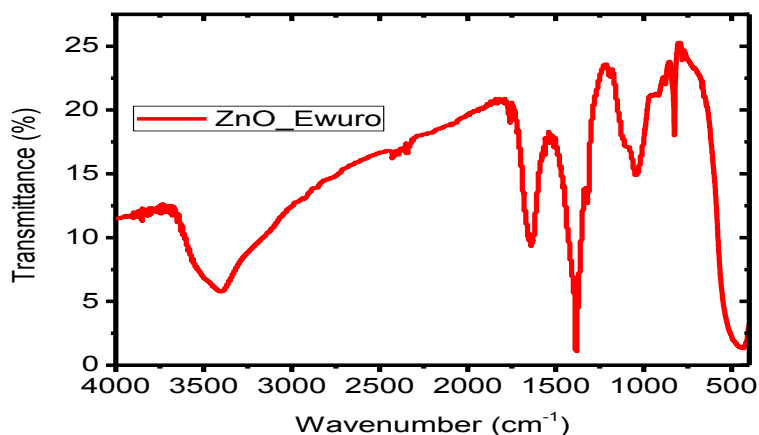


Figure 6: FTIR spectrum of biosynthesized ZnONPs

The absorption/transmission bands of metal oxides generally occur in the fingerprint region, i.e. between 400 cm^{-1} and 1500 cm^{-1} arising from inter-atomic vibrations [36]. The peaks observed at 3400 cm^{-1} and 1050 cm^{-1} could be due to O-H stretching and deformation, respectively. The peaks at 1650 cm^{-1} and 725 cm^{-1} correspond to Zn-O stretching and deformation vibration, respectively. The metal-oxygen frequencies observed for the respective metal oxides are in accordance with literature [38,39]. Kumar and Rani [36] reported similar FTIR spectra observed for zinc oxide nanoparticles in their investigation.

3.6 Performance of Solar cell based on biosynthesized and synthetic ZnONPs

Dye-sensitized solar cells based on green-synthesized and synthetic ZnONPs were fabricated using black cherry as active material. Both cells have the same I_{sc} of 18.05 mA but different V_{oc} , as shown in Figure 7, of 0.4147 V and 0.3900 V for bio-synthesized (CBd) and synthetic (CSd) ZnONPs, respectively. The data obtained from I-V measurement for both biosynthesized and synthetic based solar cells are shown in Table 1. Decrease in V_{oc} as seen in the CSd based cell could be attributed to very high series resistance of the cell [38]. In addition, imperfection on the film surface could lead to lower V_{oc} in the cell. The η of CBd and CSd based cells are 0.703 and 0.627 %.

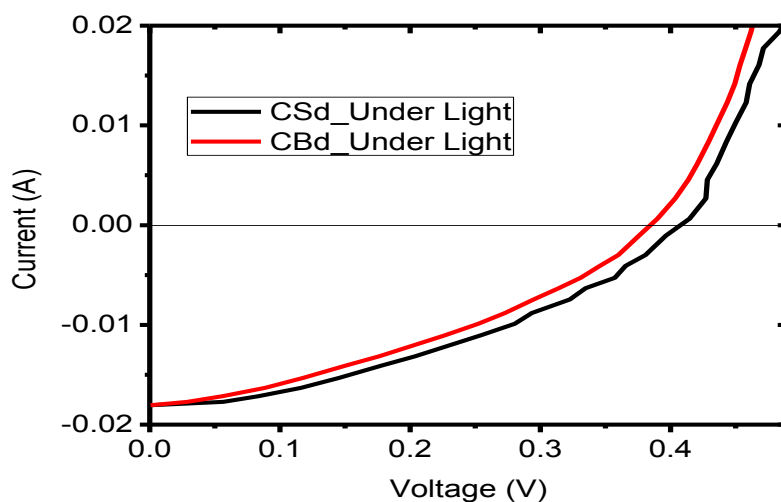


Figure 7: I-V curves of DSSC based on biosynthesized (CBd) and synthetic (CSd) ZnONPs

Table 1: I-V values from the fabricated cells based on biosynthesized (CBd) and synthetic (CSd) ZnONPs

Dye	V _{oc} (V)	I _{sc} (mA)	P _{max}	FF	η (%)
CBd	0.39	18.05	2.53	0.36	0.63
CSd	0.41	18.05	2.81	0.38	0.70

Conclusion

The experimental results reported in this paper revealed that biosynthesized ZONPs from *Vernonia Amygdalina* leaf could be potential of anti-UV in solar cell. The dye extract absorbs UV radiation and allows visible light to pass through in significant amount.

Both biosynthesized and synthetic ZnONPs were deployed in solar cells as window layer and it was observed that cell based on biosynthesized ZnONPs has power conversion efficiency of 0.63% comparable with synthetic ZnONPs based solar cell of 0.70%.

The deployment of the both ZnONPs in solar cell allowed us to establish that there could be grain boundaries in biosynthesized ZnONP which lowered performance of the cell. Therefore, it is found the eco-friendly-biosynthesized ZnONPs could be synthesized from *Vernonia Amygdalina* leaf and perform comparable with synthetic ZnONPs when deployed in solar cell as window layer.

References

1. C. S. Ezike, G. M. Z. Kana, A. O. Aina, Progress and Prosect on Stability of Perovskite Photovoltaics, *J. Mod. Mater.* 4(1) (2017) 16-30.
2. S. C. Ezike, E. Ike, J. F. Wansah, Study Effects of Ammonium Solution on Chemical Bath As-Deposited Copper Aluminum Diselenide Thin Films, *Int. J. Sci. Eng. Res.* 6(4) (2015) 1874-1888
3. P. A. Owusu, S. Asumadu-Sarkodie, A review of renewable energy sources, sustainability issues and climate change mitigation, *Cogent Engineering*, 3(1) (2016) 1167990 doi.org/10.1080/23311916.2016.1167990
4. D. Vatansever, V. Siores, T. Shah, Alternative Resources for Renewable Energy: Piezoelectric and Photovoltaic Smart Structures, Global Warming - Impacts and Future Perspective, Bharat Raj Singh, *IntechOpen* (2012). <https://doi.org/10.5772/50570>.
5. P. Sutradhar, M. Saha, Green synthesis of zinc oxide nanoparticles using tomato (*Lycopersicon esculentum*) extract and its photovoltaic application, *J. Exp. Nanosci.* 11(5) (2016) 314-327.
6. H. Kim, A. Pique, J. S. Horwitz, H. Murata, Z. H. Kafafi, C. M. Gilmore, D. B. Chrisey, Effect of aluminum doping on zinc oxide thin films grown by pulsed laser deposition for organic light-emitting devices, *Thin Solid Films* 377-378 (2000) 798-802.
7. Z. L. Wang, Zinc oxide nanostructures: growth, properties and applications, *J. Phys Condens Matter* 16 (2004) 829-858.
8. J. Wang, V. Sallet, F. Jomard, et al. Influence of substrate temperature on N-doped ZnO films deposited by RF magnetron sputtering, *Thin Solid Films* 515 (2007) 8785-8788.
9. N. Sekine, C. H. Chou, W. L. Kwan, Y. Yang, ZnO nano-ridge structure and its application in inverted polymer solar cell, *Org. Electronics* 10(8)(2009)1473-1477.
10. M. Suche, S. Christoulakis, K. Moschovis, N. Katsarakis, G. Kiriakidis, ZnO transparent thin films for gas sensor applications, *Thin Solid Films* 515(2) (2006) 551-554.
11. P. Chesler, C. Hornoiu, S. Mihaiu, et al., Nanostructured SnO₂-ZnO composite gas sensors for selective detection of carbon monoxide, *Beilstein J. Nanotech.* 7 (2016) 2045-2056.
12. Y. Zhang, T. R. Nayak, H. Hong, W. Cai, Biomedical Applications of Zinc Oxide Nanomaterials, *Curr Mol Med.* 13(10) (2013) 1633-1645.

13. Z. L. Wang, J. Song, Piezoelectric nanogenerators based on zinc oxide nanowire arrays, *Science* 312(5771) (2006) 242–246.
14. D. Bao, H. Gu, K. Anxiang, Sol-gel derived c-axis oriented ZnO thin films, *Thin Solid Films* 314(1-2) (1998) 37-39.
15. C. T. Lee, Fabrication Methods and Luminescent Properties of ZnO Materials for Light-Emitting Diodes, *Materials (Basel)* 3(4) (2010) 2218–2259.
16. T. Bora, H. H. Kyaw, S. Sarkar, S. K. Pal, J. Dutta, Highly efficient ZnO/Au Schottky barrier dye-sensitized solar cells: Role of gold nanoparticles on the charge-transfer process, *Beilstein J Nanotech.* 2 (2011) 681-690. doi: 10.3762/bjnano.2.73
17. M. R. A. Cruz, O. Ceballos-Sanchez, E. Luévano-Hipólito, L. M. Torres-Martínez, ZnO thin films deposited by RF magnetron sputtering: Effects of the annealing and atmosphere conditions on the photocatalytic hydrogen production, *Int. J. Hydrogen Energ.* 43(22) (2018) 10301-10310.
18. A-J. Cheng, Y. Tzeng, Y. Zhou, M. Park, T-H. Wu, C. Shannon, D. Wang, W. Lee, Thermal chemical vapor deposition growth of zinc oxide nanostructures for dye-sensitized solar cell fabrication, *Appl Phys Lett* 92(9) (2008) 092113 - 092113-3
19. M. Tsoutsouva, C. N. Panagopoulos, D. Papadimitriou, M. Kompitas, I. Fasaki, ZnO thin films prepared by pulsed laser deposition, *Mat. Sci. Eng. B* 176(6) (2011) 480-483
20. K. E. Kim, S-R. Jang, J. Park, R. Vittal, K-J. Kim, Enhancement in the performance of dye-sensitized solar cells containing ZnO-covered TiO₂ electrodes prepared by thermal chemical vapor deposition *Sol. Energ. Mat. Sol. Cells* 91(4) (2007) 366-370
21. S. A. Kamaruddin, K-Y. Chan, H-K. Yow, M. Z. Sahdan, H. Saim, D. Knipp, Zinc oxide films prepared by sol-gel spin coating technique, *Applied Physics A* 104(1)(2011) 263–268
22. M. I. Khan, K. A. Bhatti, R. Qindeel, N. Alonizan, H. S. Althobaiti, Characterizations of multilayer ZnO thin films deposited by sol-gel spin coating technique, *Results in Physics* 7 (2017) 651-655
23. C. E. Benouis, A. Sanchez-Juarez, M. S. Aida, Physics Properties Comparison Between Undoped ZnO and AZO, IZO Doped Thin Films Prepared By Spray Pyrolysis, *J. Appl. Sci.* 7(2) (2007) 220-225.
24. V. N. Kalpana, V. D. Rajeswari, A Review on Green Synthesis, Biomedical Applications, and Toxicity Studies of ZnO NPs *Bioinorg. Chem. Appl.*, 2018 (2018) <https://doi.org/10.1155/2018/3569758>
25. N. A. Al-Dhabi, M. V. Arasu, Environmentally-Friendly Green Approach for the Production of Zinc Oxide Nanoparticles and Their Anti-Fungal, Ovicidal, and Larvicidal Properties, *Nanomaterials (Basel)* 8(7) (2018). doi: 10.3390/nano8070500
26. J. Singh, T. Dutta, K-H. Kim, M. Rawat, P. Samddar, P. Kumar, Green synthesis of metals and their oxide nanoparticles: applications for environmental remediation, *J. NanoTech.* 16 (84)(2018). <https://doi.org/10.1186/s12951-018-0408-4> ,
27. J. Jiang, J. Pi, J. Cai, The Advancing of Zinc Oxide Nanoparticles for Biomedical Applications *Bioinorg. Chem. Appl.* 2018(2018) <https://doi.org/10.1155/2018/1062562>
28. P. Malik, R. Shankar, V. Malik, N. Sharma, T. K. Mukherjee, Green Chemistry Based Benign Routes for Nanoparticle Synthesis, *J. Nanoparticles* 2014 (2014) <http://dx.doi.org/10.1155/2014/302429>
29. C. Jayaseelan, A.A. Rahuman, A. V. Kirthi, S. Marimuthu, T. Santhoshkumar, A. Bagavan, K. Gaurav, L. Karthik, K. V. Rao, Novel microbial route to synthesize ZnO nanoparticles using *Aeromonas hydrophila* and their activity against pathogenic bacteria and fungi, *Spectrochim Acta A Mol Biomol Spectrosc.* 90 (2012) 78-84. [doi:10.1016/j.saa.2012.01.006](https://doi.org/10.1016/j.saa.2012.01.006)

30. J. Vaishnav, V. Subha, S. Kirubanandan, M. Arulmozhi, S. Renganathan, Green Synthesis of Zinc Oxide Nanoparticles by *Celosia Argentea* and Its Characterization, *J. Optoelect. Biomed. Mater.* 9(1) (2017) 59-71.
31. Q. Zhang, Y. Zhao, Z. Jia, Z. Qin, L. Chu, J. Yang, J. Zhang, W. Huang, X. Li, High stable, transparent and conductive ZnO/Ag/ZnO nanofilm electrodes on rigid/flexible substrates, *Energies* 9(6) (2016) 443 doi :10.3390/en9060443
32. S. C. Ezike, D. N. Okoli, Deposition Temperature Effects on CuAlSe₂ Compound Thin Films Prepared by Chemical Bath Deposition Technique, *IOSR J. Appl. Phy.* 1(3) (2012) 23-26
33. P. J. Lu, S. W. Fang, W. L. Cheng, S. C. Huang, M. C. Huang, H. F. Cheng, Characterization of titanium dioxide and zinc oxide nanoparticles in sunscreen powder by comparing different measurement methods, *Journal of Food and Drug Analysis* 26(3) (2018) 1192-1200
34. R. Karmakar, S. K. Neogi, A. Banerjee, S. Bandyopadhyay, Structural, Morphological, Optical and Magnetic Property of Mn doped Ferromagnetic ZnO thin film, *S. Appl. Surf. Sci.* 263 (2012), 671–677. doi:10.1016/j.apsusc.2012.09.133
35. S. Saravanan, R.S. Dubey, Study of Al-Doped and Al/N Co-Doped TiO₂ Nanoparticles for Dye Sensitized Solar Cells, *J. Mater. Environ. Sci.* 11(1) (2020) 8-14
36. H. Kumar, R. Rani, Structural and Optical Characterization of ZnO Nanoparticles Synthesized by Microemulsion Route, *Int. Lett. Chem., Phys and Astronomy* 14 (2013) 26-36.
37. A. Sadatzadeh, F. R. Charati, R. Akbari, H. H. Moghaddam, Green biosynthesis of zinc oxide nanoparticles via aqueous extract of cottonseed, *J. Mater. Environ. Sci.* 9(10) (2018) 2849-2853
38. C. N. R. Rao, Chemical Applications of Infrared spectroscopy, Academic Press, New York and London, 1963.
39. I. Markova-deneva, Infrared Spectroscopy Investigation of Metallic Nanoparticles Based on Copper, Cobalt, and Nickel Synthesized through Borohydride Reduction Method, *J. Uni. Chem. Tech. and metallurgy* 45 (2010) 351-378.

(2020) ; <http://www.jmaterenvirosci.com>